



Double, double boil and bubble: Fluidization in reactors and roasters

Paul den Hoed
5 June 2009


Modes of gas-solid contact

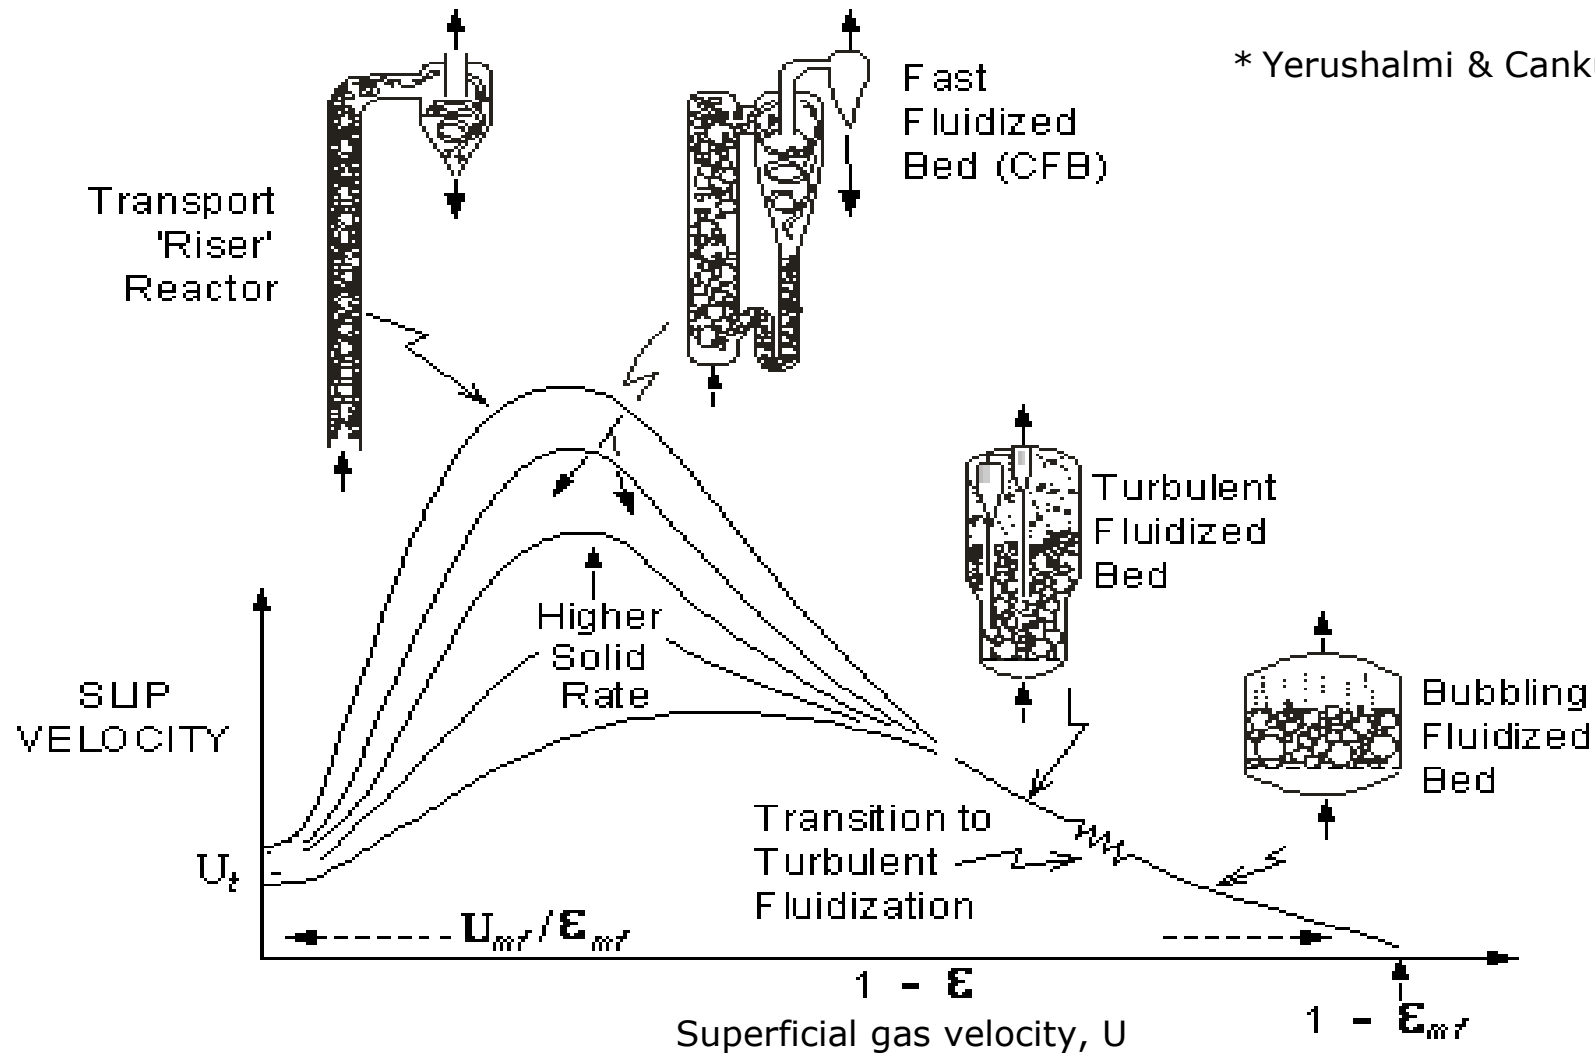

The circulating fluidized bed (CFB)

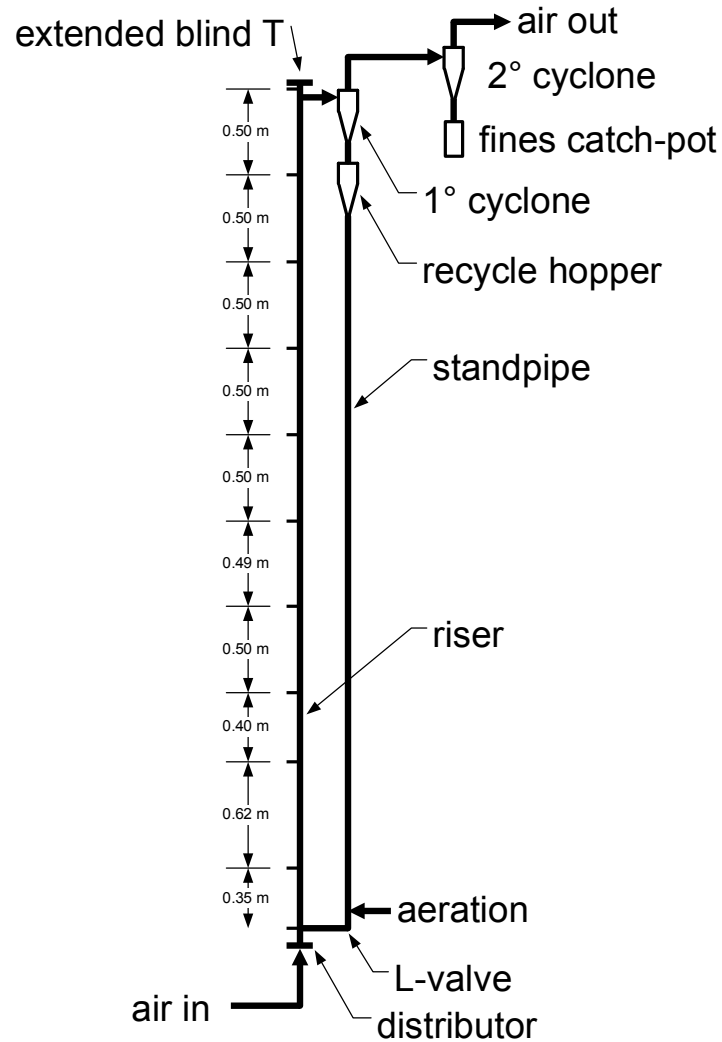

* Rutile (TiO_2), $U = 5 \text{ m/s}$

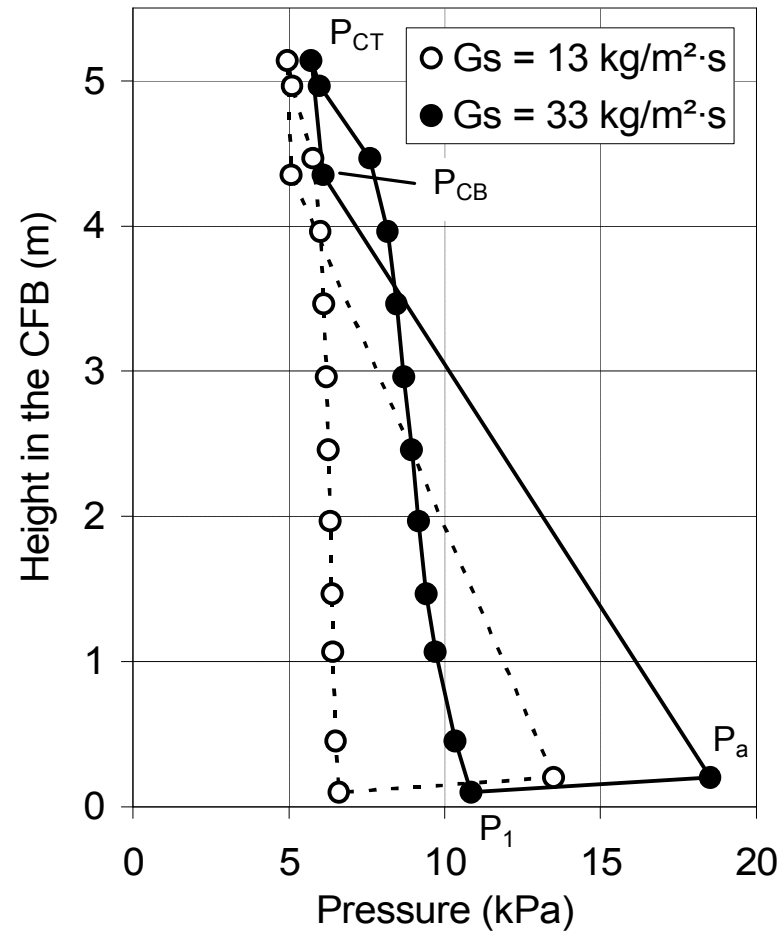


Fluidized-bed reactors and roasters can—

- Handle and process fine materials
- Burn discard coals, waste and biomass
- Lower pollutant emissions
- Offer the possibility of utilizing energy more efficiently

Fluidized-bed reactors and roasters can—

- Handle and process fine materials
 - Direct reduction of iron (DRI) Siemens-VAI and Outotec
 - A world market of ~60 Mt per annum
 - The annual production of steel totals 1,400 Mt
 - Kumba Iron Ore produces 35 Mt of iron ore a year
 - It sits with ~ Mt of fines (-6 mm)
- Burn discard coals, waste and biomass
 - CFB boilers Foster Wheeler and Alstom
 - Anglo Coal produces 96 Mt coal a year
 - It sits with ~65 Mt of discard coal
- Lower pollutant emissions
- Offer the possibility of utilizing energy more efficiently

Describing fluidization: A classification

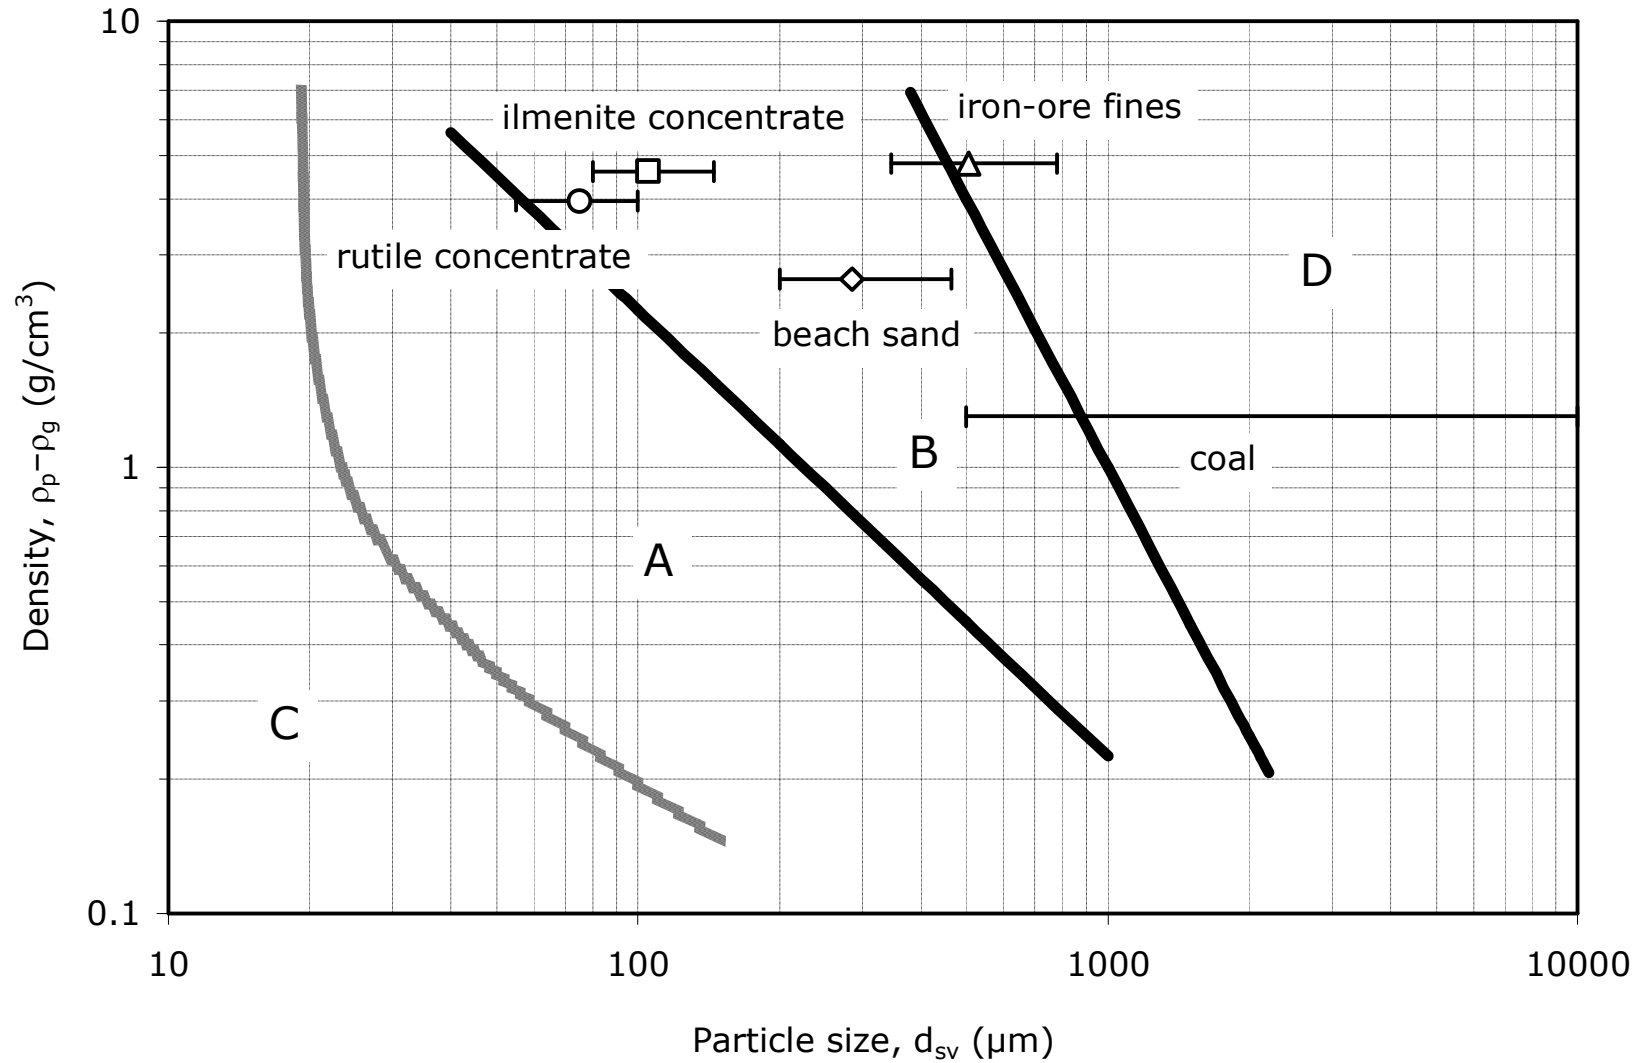


- Variables:
 - Particle size—Sauter mean diameter (d_{SV}), d_{10} and d_{90}
 - Particle density
 - Sphericity ($0 < \Phi_s \leq 1$)
 - Bed voidage ($0 < \varepsilon < 1$)
 - Gas density and gas viscosity
- Critical velocities:
 - Minimum fluidizing velocity, U_{mf}
 - Minimum bubbling velocity, U_{mb}
 - Transport velocity, U_{tr}
 - Terminal velocity, U_t


- Dimensionless numbers:
 - Reynolds number, $Re = \rho_p \cdot U \cdot d_p / \mu$
 - Archimedes number, $Ar = d_p^3 (\rho_p - \rho_g) \cdot \rho_g \cdot g / \mu^2$
- Conditions at minimum fluidization—the Ergun equation:
 - $K_1 \cdot Re_{mf}^2 + K_2 \cdot Re_{mf} = Ar$
 - For small particles ($Re_{mf} < 20$), an approximation—
 - $K_2 \cdot Re_{mf} = Ar$
- Conditions at the transport velocity:
 - $Re_{tr} = a \cdot Ar^b$
- For a single particle falling at terminal velocity:
 - $U_t = [4 \cdot d_{10} (\rho_p - \rho_g) \cdot g / (3 \cdot \rho_g \cdot C_D)]^{1/2}$

- A disparity:
 - South Africa and Australia produce 50% of the world's TiO_2 feedstock
 - They produce only 5% of the world's TiO_2 pigments and no metal
- The chloride process—
 - Produces TiCl_4
 - Chlorinators are bubbling fluidized beds
 - Temperatures run at 1000°C


* Kunii & Levenspiel, 1991

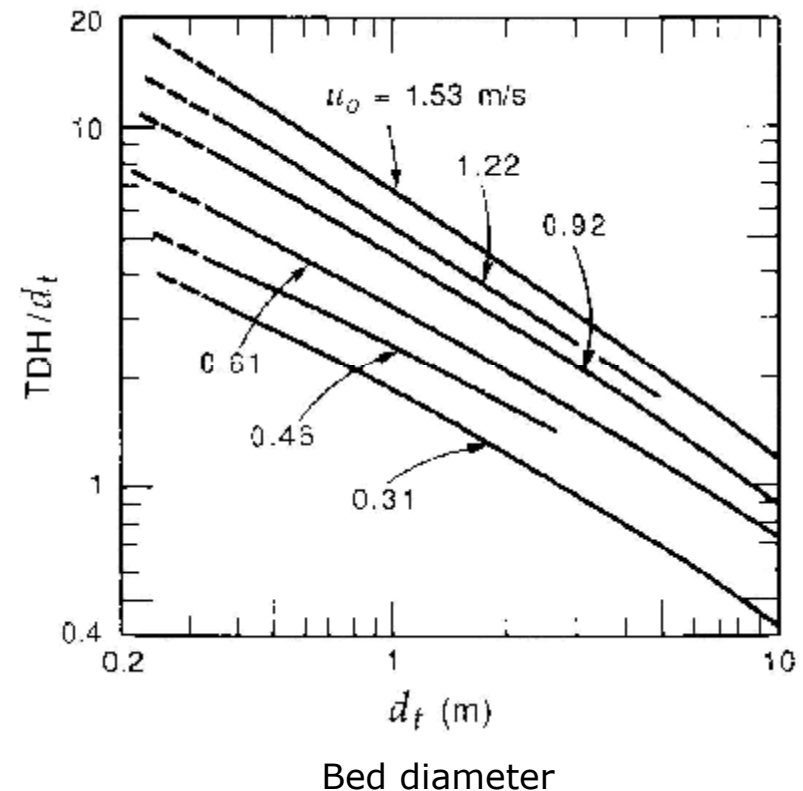

* TDH = transport disengaging height

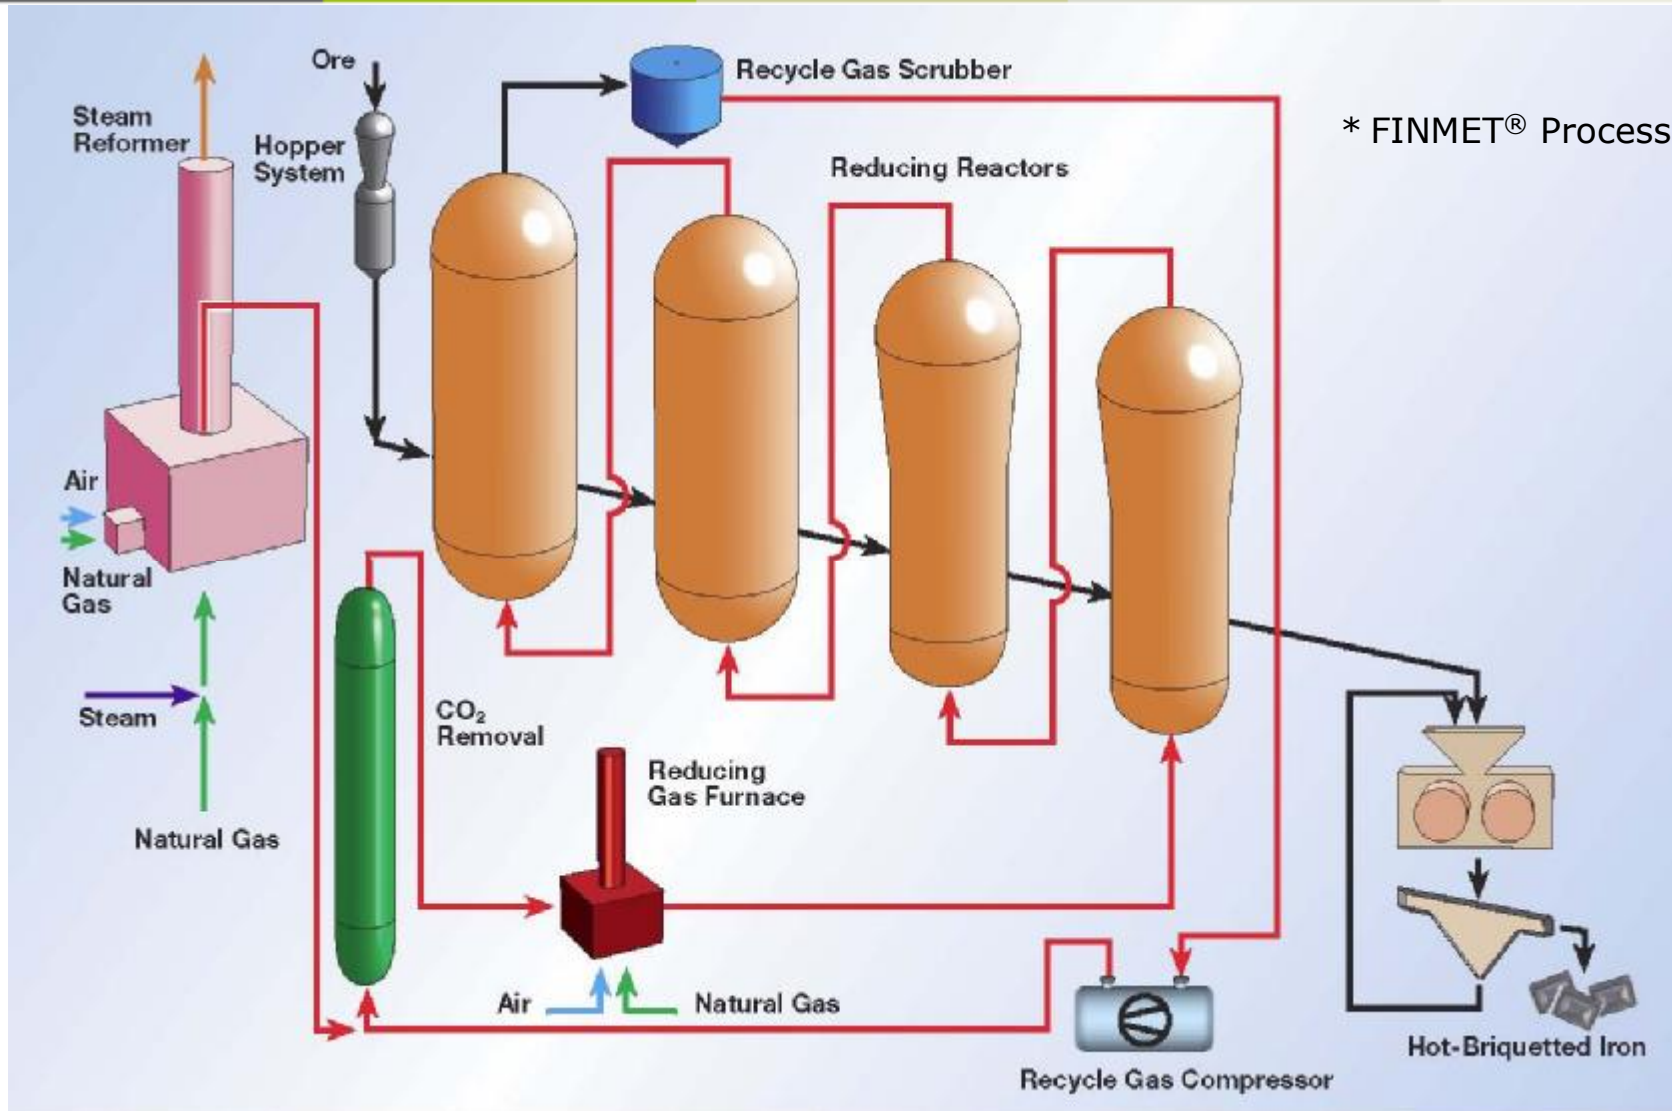

Fluidized beds in DRI

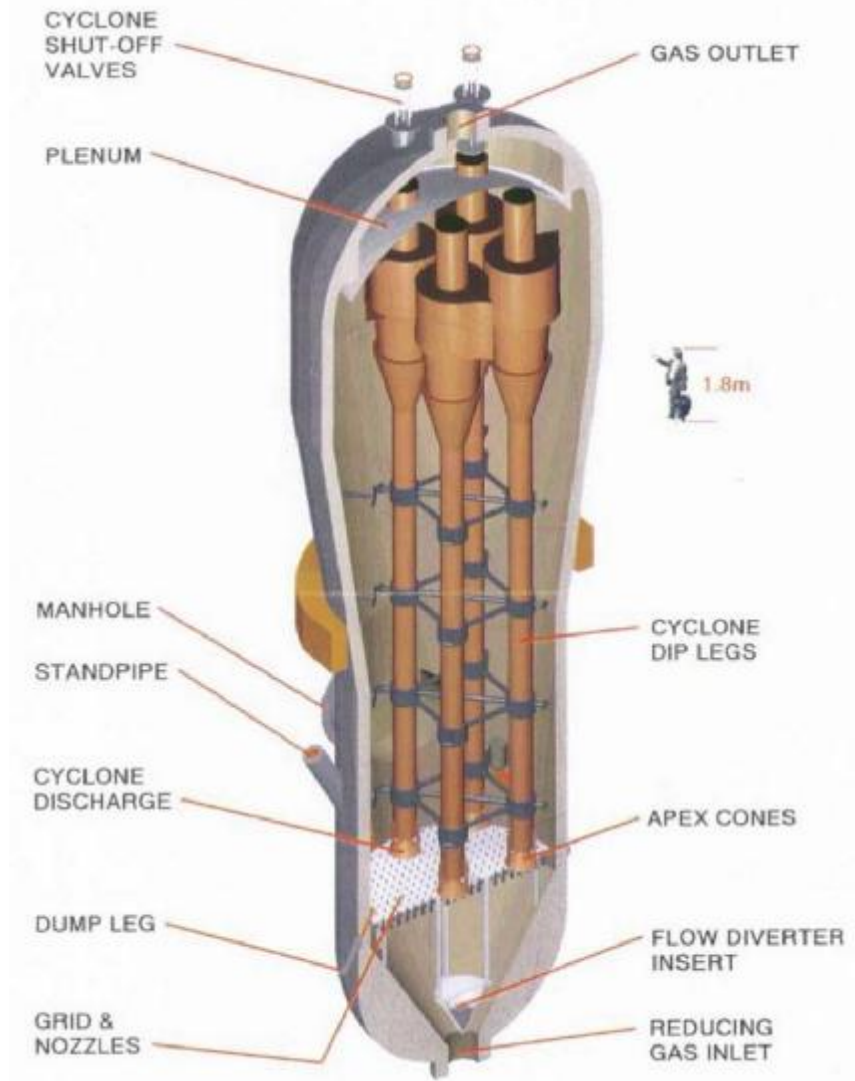

* FINMET® Process
Reactors 1 and 2


Temperature . . . 400–800°C
Pressure . . . 12 bar (gauge)
U 1–4 m/s
50 μm < d_p < 8 mm

* Schenk, 2008


Outokumpu process

- Chromite fines are pelletized
- Feed is preheated to 600–700°C
- Submerged-arc furnace


* Base case

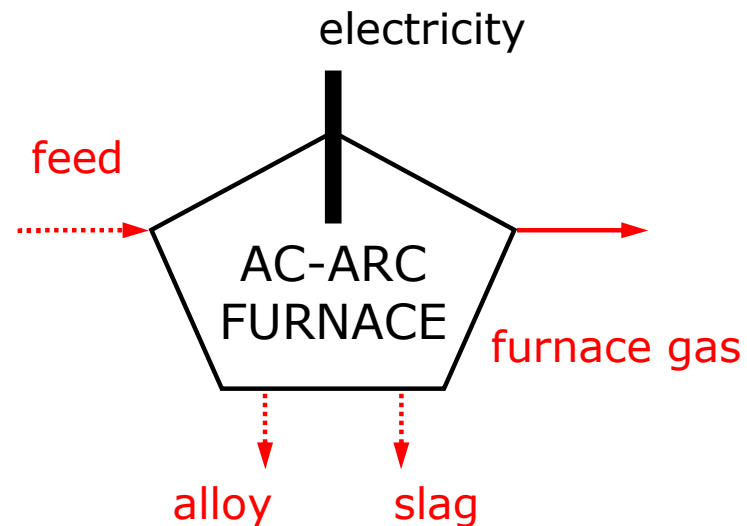

* Scenario 1

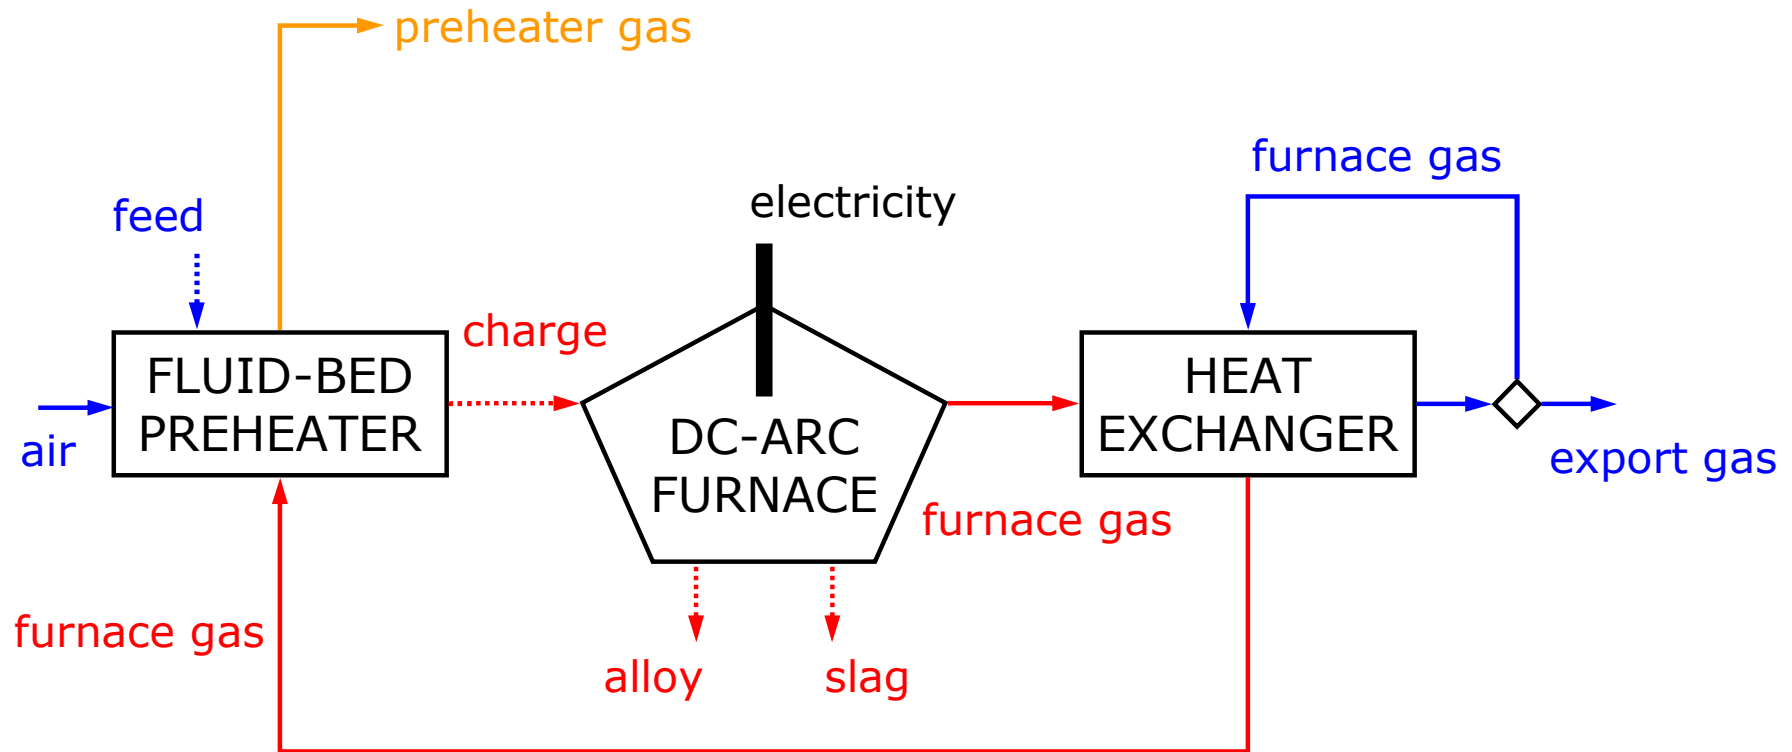

* Scenario 2

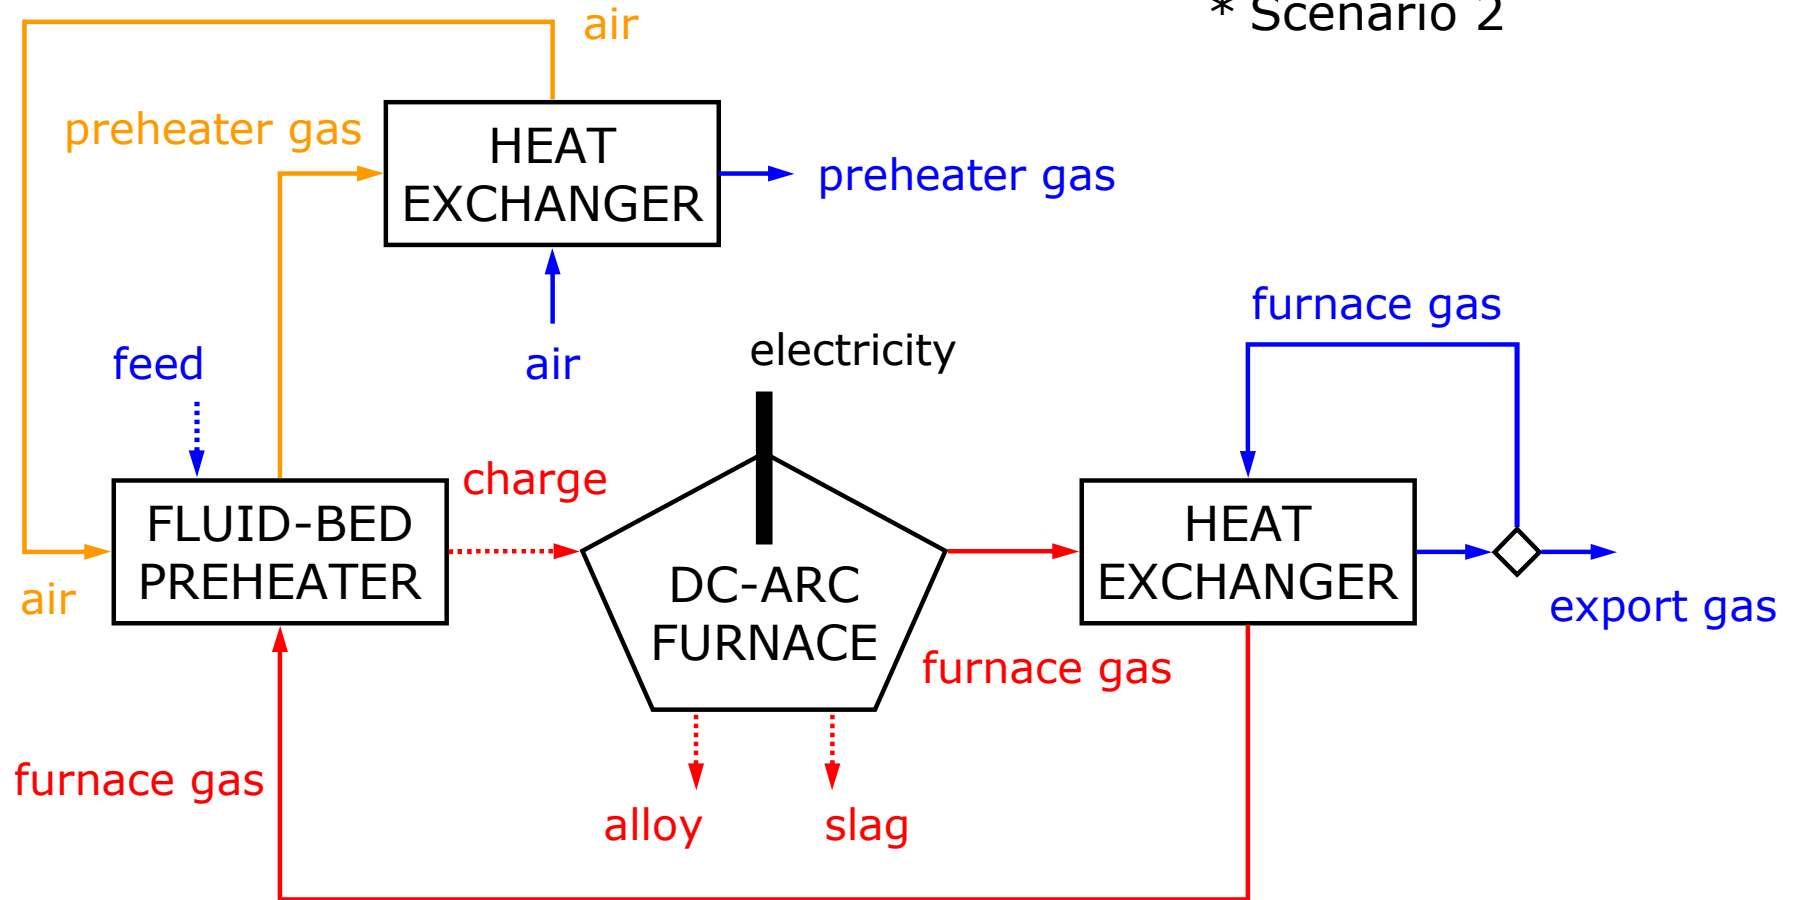

	Base case	Scenario 1	Scenario 2
Furnace power(MW)	63	48	48
Process energy (MWh/t alloy)	4.0	2.9	2.9
Furnace off-gas (kt/a)	131	131	131
Gas to preheater (kt/a)	—	92	66
Air to preheater (kt/a)	—	224	160
Preheater off-gas (kt/a)	—	330	241
Export gas (kt/a)	—	36	62